



**HAL**  
open science

## Coating carbon nanotubes with a polystyrene-based polymer protects against pulmonary toxicity.

Lyes Tabet, Cyrill Bussy, Ari Setyan, Angélique Simon-Deckers, Michel Rossi,  
Jorge Boczkowski, Sophie Lanone

### ► To cite this version:

Lyes Tabet, Cyrill Bussy, Ari Setyan, Angélique Simon-Deckers, Michel Rossi, et al.. Coating carbon nanotubes with a polystyrene-based polymer protects against pulmonary toxicity.. Particle and Fibre Toxicology, 2011, 8 (1), pp.3. 10.1186/1743-8977-8-3 . inserm-00649416

**HAL Id: inserm-00649416**

**<https://inserm.hal.science/inserm-00649416>**

Submitted on 7 Dec 2011

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

RESEARCH

Open Access

# Coating carbon nanotubes with a polystyrene-based polymer protects against pulmonary toxicity

Lyes Tabet<sup>1</sup>, Cyrill Bussy<sup>1</sup>, Ari Setyan<sup>2,6</sup>, Angélique Simon-Deckers<sup>1</sup>, Michel J Rossi<sup>3</sup>, Jorge Boczkowski<sup>1,2,5†</sup>, Sophie Lanone<sup>1,3,4,5\*†</sup>

## Abstract

**Background:** carbon nanotubes (CNT) can have adverse effects on health. Therefore, minimizing the risk associated with CNT exposure is of crucial importance. The aim of this work was to evaluate if coating multi-walled CNT (MWCNT) with polymers could modify their toxicity, thus representing a useful strategy to decrease adverse health effects of CNT. We used industrially-produced MWCNT uncoated (NT1) or coated (50/50 wt%) with acid-based (NT2) or polystyrene-based (NT3) polymer, and exposed murine macrophages (RAW 264.7 cell line) or Balb/c mice by intratracheal administration. Biological experiments were performed both *in vitro* and *in vivo*, examining time- and dose-dependent effects of CNT, in terms of cytotoxicity, expression of genes and proteins related to oxidative stress, inflammation and tissue remodeling, cell and lung tissue morphology (optical and transmission electron microscopy), and bronchoalveolar lavage fluid content analysis.

**Results:** extensive physico-chemical characterization of MWCNT was performed, and showed, although similar dimensions for the 3 MWCNT, a much smaller specific surface area for NT2 and NT3 as compared to NT1 (54.1, 34 and 227.54 m<sup>2</sup>/g respectively), along with different surface characteristics. MWCNT-induced cytotoxicity, oxidative stress, and inflammation were increased by acid-based and decreased by polystyrene-based polymer coating both *in vitro* in murine macrophages and *in vivo* in lung of mice monitored for 6 months.

**Conclusions:** these results demonstrate that coating CNT with polymers, without affecting their intrinsic structure, may constitute a useful strategy for decreasing CNT toxicity, and may hold promise for improving occupational safety and that of general the user.

## Background

Carbon nanotubes (CNT) exhibit unique properties, including mechanical, thermal and electrical conductivity, as well as field emission properties. These properties are associated with many applications (car industry, sport accessories, ...), and lead to a steady increase in the industrial production of CNT. However, it is increasingly obvious that exposure to nanoparticles in general, and CNT in particular, can have adverse effects on human health, especially at the level of the pulmonary system, which is a primary route of exposure [1].

This is raising considerable concern [2-9]. Therefore, minimizing the risk associated with CNT exposure is of crucial importance.

Among adverse health effects secondary to exposure to CNT, inflammation and oxidative stress are particularly worrisome because they can be associated with tissue remodeling and impaired function and/or carcinogenesis [10]. Recent data show that the length and rigidity of the nanotubes influences the pro-inflammatory effect of CNT [11]. However, the possible influence of other physicochemical properties remains incompletely understood [12]. Since surface characteristics influence the pro-inflammatory effect of spherical nanoparticles [13], we hypothesized that embedding CNT in polymers, thus modifying the surface environment of those CNT, could modify their toxicity, and thus represent a useful

\* Correspondence: sophie.lanone@inserm.fr

† Contributed equally

<sup>1</sup>INSERM U955, Créteil, F-94010 France, and Université Paris Est Val de Marne (UPEC), Créteil, F-94010, France

Full list of author information is available at the end of the article

strategy to decrease adverse health effects of industrially-produced CNT, without affecting their specific properties and further applications. The protective effect of the compatible solute Ectoine against carbon nanoparticle-induced lung inflammation has been nicely demonstrated recently [14]. However, a strategy based on the production of intrinsically safer nanomaterials seems to be much more promising. Such an approach is essential to the further development and safe use of CNT, at an occupational level as well as at the level of the general user.

To assess our hypothesis, we utilized an original approach by coating industrially produced multi-walled CNT (MWCNT) with two different polymers (acid-based and polystyrene-based, respectively) that resulted in different surface environment but similar specific surface areas. To the best of our knowledge, although surface modifications is important to CNT toxicity [15-19], polymer coating has never been used before as an approach to modulate CNT toxicity. Coating could represent a useful tool, as it allows modifying CNT's external surface environment, without affecting their intrinsic structure. We investigated whether coating modified the toxicity of MWCNT *in vitro* in murine macrophages and *in vivo* in mice monitored for 6 months after intratracheal MWCNT instillation. Here, we report that MWCNT-induced cytotoxicity, oxidative stress, and inflammation in both models were increased by acid-based polymer coating and decreased by polystyrene polymer coating. These results demonstrate that surface characteristics play a major role in the biological response to CNT and that modifications of the surface environment by coating with specific compounds may constitute a useful strategy for decreasing CNT toxicity, without affecting their intrinsic structure, already at the time of their production. This may therefore hold promise for improving occupational safety as well as that of general users.

## Methods

We investigated the effects of industrially-produced MWCNT that were either uncoated (NT1) or coated with carboxylic polyacid polymer (NT2) or a hydrophobic polystyrene polybutadiene polymethylmethacrylate polymer (NT3). These MWCNT were provided by ARKEMA-France (Colombes, France). The two coated MWCNT were composed of 50% MWCNT and 50% coating polymer by weight (determined by Thermo Gravimetric Analysis). Coatings were performed as follows; both coated MWCNT were produced by impregnation of NT1 powder (50% weight) with a solution of polymer (carboxylic polyacid polymer for NT2, and polystyrene polybutadiene polymethylmethacrylate for NT3), the solvent being thereafter eliminated by drying

under vacuum conditions. Solvent was water for NT2, and methyl ethyl cetone for NT3. NT2 remained coated after dispersion in the culture medium, as revealed by the Toluidine Blue (TB) assay, which measures the stability of polymer grafting [20] (data not shown). Briefly, a  $5 \cdot 10^{-4}$  M TB aqueous solution was prepared and 0.2 ml of a buffer solution of 2-amino 2-methyl propanol was added to reach and maintain the solution pH value at 10. Each MWCNT sample was placed in TB solution at 30°C up to 24 hours. At different time points, uncomplexed TB molecules were removed by rapid washing (30 minutes) of the sample by a basic aqueous solution (NaOH  $5 \cdot 10^{-4}$  M, pH 9). Then, each sample was in 10 ml of an aqueous acetic acid solution (50% v/v) for 24 hours to obtain complete decomplexation of TB from the sample. The decomplexation solution was analyzed by UV/visible spectroscopy at 633 nm. There was no chemical link between the polymers and the nanotubes.

Both coated NT (NT2 and NT3) appear as powders, as the pristine one (NT1), and were dispersed in culture medium for both *in vitro* and *in vivo* experiments. The two polymers were also dispersed in culture medium in order to assess their intrinsic effects.

The effects of the three MWCNT were compared to those of crocidolite asbestos fibres (80 nm in diameter) kindly donated by Dr. Ghislaine Lacroix (INERIS, Verneuil-en-Hallatte-France) and of nanosized carbon black (CB, FR103, 95 nm in diameter; Degussa, Dusseldorf, Germany).

We chose to study industrially-produced MWCNT to obtain results relevant to occupational health, in the context of increasing industrial development and use of CNT.

## Physicochemical characterization of multi-walled carbon nanotubes

MWCNT dimensions were measured using transmission electron microscopy (TEM), and MWCNT morphology was observed using scanning electronic microscopy (SEM). Chemical composition and carbon content were determined using inductively coupled plasma mass spectroscopy (ICP-MS), electron spectroscopy for chemical analysis (ESCA). Specific surface area was measured using Brunauer Emmett Teller (BET) adsorption isotherms of nitrogen at 77 K. Surface functional groups were identified by surface titration using six probe gases flowing across a Knudsen flow reactor [21-23]. The relative uncertainty for both values (substrate/probe gas pair) is typically 25%.

## Particle suspensions

All particles were suspended at 10 mg/ml in Dulbecco's modified Eagle medium (DMEM). We choose not to disperse CNT using any particular agent because our

aim was to examine the biological effects of surface properties of coated and uncoated CNT without any other interference. The suspensions were then vortexed for 1 min, and sonicated (Elma S30H, 50-60 Hz) for 30 min under cooling conditions, with a 30-s interruption every 10 min with the vortex at maximum speed. Immediately after the end of sonication, the particle solutions were vortexed again for 1 min at maximum speed and diluted to various concentrations in culture medium (see below). CNT dispersion was quantified by dynamic light scattering using a Zetasizer Nano S (Malvern Instruments Ltd, Worcestershire, UK). Under control conditions, cells were cultured in serum-free DMEM without the particles (see below).

### In Vitro Studies

#### a. RAW 264.7 macrophage culture and exposure

RAW 264.7 murine macrophages were purchased from the American Type Culture Collection (Manassas, VA), and were cultured as previously described [24]. Cells were exposed for 6 or 24 hours to 0.1 to 100 µg/ml (0.02-20 µg/cm<sup>2</sup>) of MWCNT or to 100 µg/ml (20 µg/cm<sup>2</sup>) of crocidolite fibres or CB nanoparticles in serum-free medium, as it is known that serum can interact with nanomaterials and modify cellular response [25].

#### b. Light microscopy

Cell morphology was assessed by light microscopy after cell staining with Harris haematoxylin-phloxin. The size and number of the agglomerates present on the cells were determined as previously described [23]. Light microscopy studies were done in blinded fashion by two independent observers (LT and CB). The coefficient of variation for each measurement was <5%.

#### c. Cell viability

Cell viability was assessed using three methods, namely the MTT and Neutral Red assays and quantification of DNA content. These tests were performed as previously described [23]. Results were expressed as the mean of at least three independent experiments, each having six replicates, given as the ratio of the mean under each

condition over the mean under the control condition (cells exposed to DMEM). Since nanomaterials may interfere with cytotoxicity tests [26], we performed the assays with and without 100 µg/ml of NT1, NT2, or NT3 during incubation with the dye, and we measured absorbance. No interference of NT1, NT2, or NT3 with any of the assays was observed (data not shown).

#### d. Transmission Electron Microscopy

Cells exposed for 24 h to 10 µg/ml of NT1, NT2, or NT3 were examined by TEM as previously described [23]. The percentage of cells with MWCNT-containing vacuoles after 24 hours' exposure to 100 µg/ml was determined on semi-fine slides. Under each stimulation condition, five fields were randomly selected from top to bottom across the vertical diameter of the sample. The measurements were made in blinded fashion by two independent observers (LT and CB). The coefficient of variation for the measurement was <5%.

#### e. Reverse Transcription and Quantitative PCR (Q-PCR)

The mRNA expression of various genes involved in oxidative stress and inflammation was measured using Q-PCR as described previously [23]. The primer sets are shown in Table 1. The expression of the gene of interest was reported as the ratio over Rpl13 expression.

### In Vivo Studies

#### a. Animal exposure

The experiments were approved by the local Institutional Animal Care and Use Committee, and the experimental protocol complied with French legislation about animal studies. Male Balb/C mice aged 7-9 weeks and weighing 22 ± 0.23 g, were purchased from Janvier (Le Genest-St-Isle, France) and housed in standard wire-topped cages in temperature-controlled units with food and water ad libitum.

NT1, NT2, or NT3 were suspended in DMEM as for the *in vitro* studies. The suspension was instilled intratracheally after anaesthesia of the animal with 1.6 mg ketamine (Merial, Lyon, France) plus 300 mg xylazine (Bayer, Puteaux, France). A single dose (10 or 100 µg/mouse) of

**Table 1 Sequences of primers used for quantitative PCR assays**

Gene	Forward Primer	Reverse Primer
<i>RPL-13</i>	GTGGTCCCTGCTGCTCTCCAA	CGATAGTGCCATCTGGCCITTT
<i>HO-1</i>	CACGCATATACCCGCTACCT	CCAGAGTGTTTCATTTCGAGCA
<i>GPX-1</i>	TGAAGAGATTCTGAATTCCTCAAG	CAGGAAGGTAAAGAGCGGGTG
<i>SOD-1</i>	CAAATTACAGGATTAAGTGAAGGCC	GGCCACCATGTTTCTTAGAGTGAG
<i>SOD-2</i>	CTACGTGAACAATCTCAACGCC	ATTAATATGTCCCCACCATTGAAC
<i>TNF-α</i>	CTGTCTACTGAACCTCGGGGTGAT	GGTCTGGCCATAGAAGTATGATG
<i>CXCL2</i>	GAACATCCAGAGCTTGAGTGTGAC	CTTGCCITTTGTTTCAGTATCTTTTGG
<i>α-2 collagen-1</i>	GGCTATGACTTTGGTTTTGAAGGA	CGTTGTCGTAGCAGGGTTCITTT
<i>α-1 collagen-3</i>	CCAGAACATTACATACCCTGCAAA	GTGTTTAGTACAGCCATCCTCTAGAAGTG

*RPL13*, ribosomal protein L13; *HO-1*, heme oxygenase-1; *SOD*, superoxide dismutase; *GPX-1*, Glutathione peroxidase-1; *CXCL2*, macrophage inflammatory protein-2; *TNF-α*, tumour necrosis factor alpha.

NT1, NT2, or NT3 was given to each animal. The highest dose was relevant to the 20  $\mu\text{g}/\text{cm}^2$  concentration used in the *in vitro* studies [27]. The mice were sacrificed 1, 7, 30, 90, or 180 days post-instillation. In a subset of experiments, animals were exposed to 200  $\mu\text{g}$  of NT2 or NT3, in order to allow adequate comparison with 100  $\mu\text{g}$  NT1.

#### **b. Bronchoalveolar Lavage (BAL) and Lung Recovery**

The mice were anesthetized with an intramuscular injection of ketamine/xylazine and sacrificed by exsanguination. BAL fluid analysis and lung tissue recovery were performed as described previously [28]. The percentage of macrophages with MWCNT-containing vacuoles was determined as for the *in vitro* studies. The mRNA expression of the genes evaluated *in vitro* was measured using Q-PCR on homogenates, with the same set of primers (Table 1). In addition, we measured the expression of collagen-1 and -3, used as markers for interstitial fibrosis.

#### **c. Histological study of lung samples**

Lung histology was examined in a subset of animals different from that used for investigating BAL fluid and lung gene expression determination. The lungs were fixed with 0.8 ml of a 1:1 mix of 0.9% saline with Tissue-Tek ornithine carbamoyltransferase fluid (Sakura, Zoeteroude, The Netherlands) and were snap-frozen in liquid nitrogen. Lung histology studies were performed as described previously [29].

The number and size of MWCNT agglomerates in the lungs of animals exposed for 24 hours, 1 month, or 6 months was measured in five representative animals per group. For each animal, five fields were randomly selected from top to bottom across the vertical diameter of the section. Calculations were performed using ImageJ software (<http://rsbweb.nih.gov/ij/>), and the analysis was performed in blinded fashion by two independent observers (LT and CB). The coefficient of variation for each measurement was <5%.

#### **Statistical Analysis**

The values from at least four different experiments (*in vitro* study) and 6-8 animals (*in vivo* study) are represented as box and whisker plots. *In vitro* experiments were

performed in triplicate. The data were analysed using the non-parametric Kruskal-Wallis test, followed by Dunn's multiple comparison test where appropriate. For all tests, *p* values smaller than 0.05 were considered significant.

## **Results**


### **Physicochemical characterization of multi-walled carbon nanotubes**

The NT1 used in this study have been extensively characterized [23]. NT2 and NT3, the two coated MWCNT were composed of 50% MWCNT and 50% coating polymer by weight. They were produced by chemical vapour deposition on a supported catalyst in a fluidized bed that yielded spheric heaps of MWCNT entangled around the supported catalyst, measuring about few hundred microns in diameter, and forming a free-flowing powder.

Typical SEM images of the various MWCNT are shown in Figure 1 and Additional file 1, figure S1. Physicochemical characterization (Table 2) showed that NT2 and NT3 had similar dimensions and metallic impurities compared to NT1. Specific surface area was similar for NT2 and NT3 and smaller than the specific surface area of NT1. Furthermore, all three MWCNT showed micrometric agglomerates in suspension (as demonstrated previously [23]), whose diameter was largest for NT1 and smallest for NT2. Surface chemical analysis of functional groups located on the surface of the MWCNT showed a larger amount of acidic sites on NT2 compared to the other two MWCNT (Table 3). Moreover both NT2 and NT3 contain a significant amount of surface carbonyl. No basic oxides are present, as seen by the ratio of the uptake of HCl/CF<sub>3</sub>COOH.

### **In vitro studies**

We first evaluated the effects of the three MWCNT on macrophages (murine cell line RAW 264.7), which play a key role in host defence mechanisms against foreign bodies. Figure 2 shows representative light microscopy images of RAW macrophages exposed for 24 h to the three MWCNT, CB, and asbestos fibres. Even after

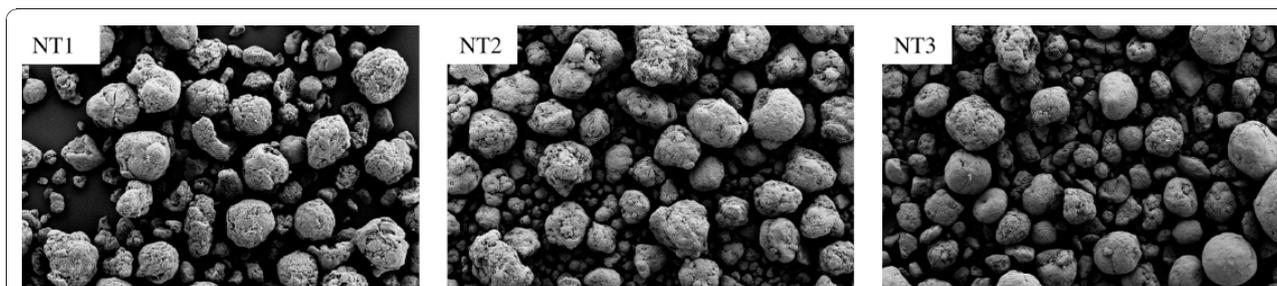

**Figure 1 SEM observations.** Representative scanning electron microscopy (SEM) image of uncoated multi-walled carbon nanotubes (NT1) and of the same nanotubes coated with carboxylic polyacid polymer (NT2) or polystyrene polybutadiene polymethacrylate polymer (NT3).

**Table 2 Physicochemical characteristics of the multi-walled carbon nanotubes (MWCNT) used in the study**

	NT1	NT2	NT3
Coating polymer (50/50 wt%)	None	Carboxylic polyacid polymer	PMMA <sup>a</sup> polymer
Diameter (nm)	12 ± 1	12 ± 1	12 ± 1
Size distribution (diameter)	0-15 nm	85%	85%
	15-30 nm	13%	13%
	>30 nm	2%	2%
Length (µm)	0.1-13	0.1-13	0.1-13
Metallic impurities	Aluminium (%)	3.2	1.15
	Iron (%)	2.45	0.75
Specific surface (m <sup>2</sup> /g)	227.4	54.1	34
Agglomerate size - mean diameter (%<10 µm)	338 (0.13)	118 (1.45)	267 (0.83)

<sup>a</sup> Polystyrene polybutadiene polymethylacrylate (PMMA).

thorough washing, MWCNT agglomerates were seen in contact with the cells. The number of these agglomerates was largest for NT2 and smallest for NT3 (Table 4). All three MWCNT were internalized by the macrophages within vacuoles, as single nanotubes or as agglomerates, without any modification of cell morphology (TEM images, Figure 3a and Additional file 2, figure S2). Quantitative analysis of internalization in vacuoles showed that the percentage of cells containing internalized nanotubes was greatest with NT2 and smallest with NT3 (Figure 3b). Few MWCNT were seen in the cytoplasm. Taken together, these results indicate stronger “attachment” to the cell surface and greater internalisation with NT2 than with NT1 or NT3, despite the similar dimensions, metallic impurities of the three MWCNT, and a specific surface similar to NT3.

Cell viability was assessed using several tests. The MTT assay showed a similar dose-dependent decrease in mitochondrial metabolism after 24 h of exposure to NT1, NT2, and crocidolite (Figure 4a). This effect was already detectable after 6 h with NT2 (Additional file 3, figure S3). No such effect was observed with NT3, CB,

or the polymers alone (data not shown). The Neutral Red assay (which measures cell membrane permeability) and DNA content quantification (which measures cell number) showed no significant alterations in cells exposed to any of the MWCNT or other materials (data not shown). The preferential effect of nanoparticles on mitochondrial metabolism has been described previously [23,30-32].

We next quantified the expression of several genes involved in inflammation and oxidative stress. Expression of the mRNAs for the antioxidant gene *HO-1* and the pro-inflammatory gene *CXCL2* was significantly increased in cells exposed to crocidolite, NT1, or NT2, compared to control cells exposed to medium alone (Figures 4b and 4c). NT1 induced a significantly greater increase in *CXCL2* expression than did NT2 ( $p < 0.05$ , Figure 4c). No such modifications occurred after cell incubation with NT3, CB or the polymers alone (data not shown). Finally, with none of the nanomaterials studied were changes seen in mRNA expression of the antioxidant genes *GPX-1*, *SOD-1*, or *SOD-2*, or of the inflammatory gene *TNF-α* (data not shown).


**Table 3 Characterization using a Knudsen flow reactor of the surface functional groups present on the multi-walled carbon nanotubes (MWCNT)**

MWCNT	Gas [gas-phase probe molecules]	N(CH <sub>3</sub> ) <sub>3</sub> [acidic sites]	HCl [basic sites]	CF <sub>3</sub> COOH [basic sites]	NH <sub>2</sub> OH [carbonyl functions]	O <sub>3</sub> [oxidisable sites]	NO <sub>2</sub> [oxidisable sites]
NT1	N°/mg <sup>a</sup>	3.0 · 10 <sup>15</sup>	8.1 · 10 <sup>16</sup>	2.4 · 10 <sup>16</sup>	2.4 · 10 <sup>17</sup>	3.9 · 10 <sup>18</sup>	1.2 · 10 <sup>16</sup>
	N°/cm <sup>2b</sup>	1.32 · 10 <sup>12</sup>	35.6 · 10 <sup>12</sup>	10.6 · 10 <sup>12</sup>	105.5 · 10 <sup>12</sup>	1715 · 10 <sup>12</sup>	5.3 · 10 <sup>12</sup>
NT2	N°/mg <sup>a</sup>	6.4 · 10 <sup>15</sup>	4.4 · 10 <sup>16</sup>	5.9 · 10 <sup>15</sup>	3.4 · 10 <sup>17</sup>	1.8 · 10 <sup>17</sup>	1.2 · 10 <sup>15</sup>
	N°/cm <sup>2b</sup>	11.8 · 10 <sup>12</sup>	81.3 · 10 <sup>12</sup>	1.1 · 10 <sup>12</sup>	628.5 · 10 <sup>12</sup>	332.7 · 10 <sup>12</sup>	2.2 · 10 <sup>12</sup>
NT3	N°/mg <sup>a</sup>	2.6 · 10 <sup>14</sup>	1.4 · 10 <sup>16</sup>	5.8 · 10 <sup>14</sup>	2.0 · 10 <sup>17</sup>	1.1 · 10 <sup>18</sup>	1.9 · 10 <sup>15</sup>
	N°/cm <sup>2b</sup>	0.8 · 10 <sup>12</sup>	41.2 · 10 <sup>12</sup>	1.7 · 10 <sup>12</sup>	588 · 10 <sup>12</sup>	3235 · 10 <sup>12</sup>	5.6 · 10 <sup>12</sup>

<sup>a</sup> Number of probe molecules taken up per mg of deposited nanoparticles.

<sup>b</sup> Number of probe molecules taken up per square cm of MWCNT (no/cm<sup>2</sup>), using the BET surface as a surface metric.

NT1, uncoated MWCNT; NT2, MWCNT coated with carboxylic polyacid polymer; NT3, MWCNT coated with polystyrene polybutadiene polymethylacrylate polymer.

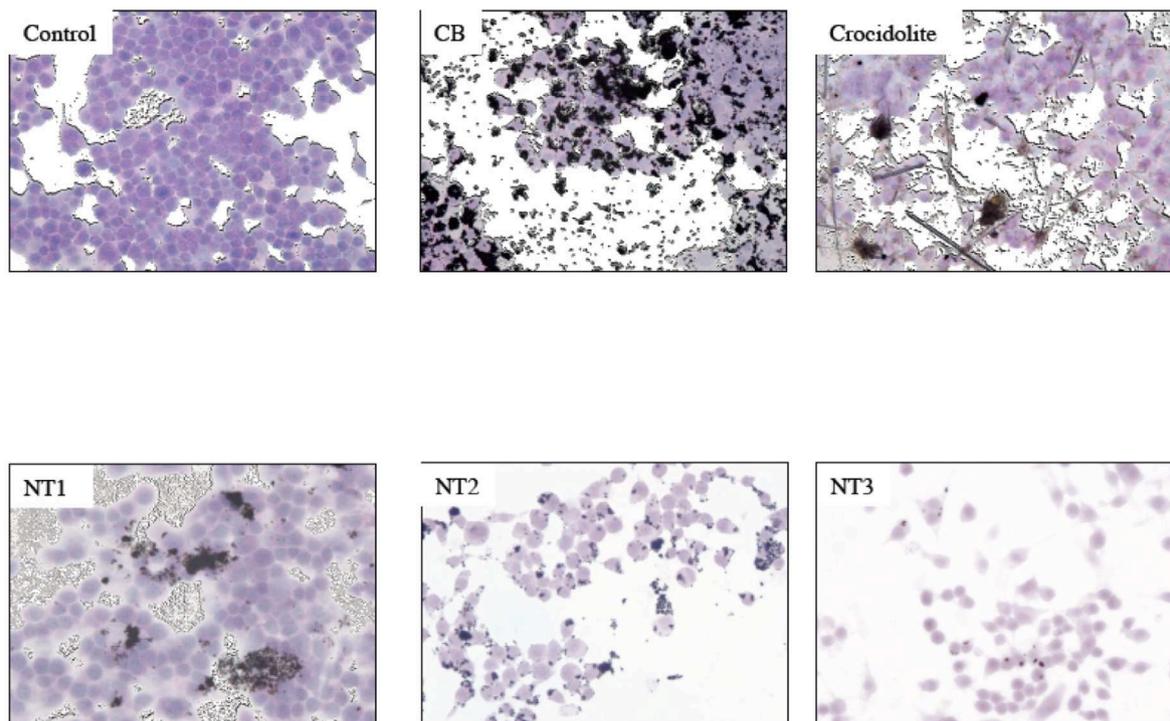

**Figure 2 Effects of MWCNT on macrophages in vitro - light microscopy observations.** Representative light microscopy images of RAW 264.7 cells exposed for 24 h to culture medium alone (Control) or 100 µg/ml of carbon black (CB), crocidolite fibres, NT1, NT2 or NT3. Original magnification: x 20. Abbreviations are the same as in Figure 1.

### In vivo studies

The relevance of the *in vitro* data was evaluated *in vivo* in Balb/c mice, each given a single intratracheal instillation of either 10 µg or 100 µg of MWCNT then monitored for up to 6 months. BAL fluid analysis showed that exposure to NT2 induced a dose-dependent increase in total cell count ( $p < 0.05$  vs. control, Figure 5a) and a significant influx of neutrophils and macrophages ( $p < 0.05$  vs. control, Figure 5b and 5c). These effects were observed 24 h post-instillation and

lasted up to 1 month. With NT1, the modifications were similar to those produced by NT2 but less marked and present only 24 h post-instillation. No significant effect was observed after administration of polymers alone (data not shown). All three MWCNT were internalized in macrophages between 1 day and 1 month after instillation (Additional file 4, figure S4). The percentage of macrophages with MWCNT-containing vacuoles was higher with NT2 than with NT1 or NT3, and was also observed between 1 day and 1 month after instillation ( $p < 0.05$ , Figure 5d). MWCNT internalization was independent from the MWCNT dose. The percentages of macrophages with MWCNT-containing vacuoles were not significantly different between NT1 and NT3.

**Table 4 Size and number of carbon nanotube agglomerates found in vitro 24 hours after exposure to multi-walled carbon nanotubes (MWCNT)**


MWCNT	Surface area (µm <sup>2</sup> )	Number/field
NT1	30.23 ± 7.32	18.5 ± 1.5
NT2	12.87 ± 3.4*	37.3 ± 3.7*
NT3	4.97 ± 1.61 <sup>#</sup>	9.3 ± 1.9 <sup>#</sup>

\*:  $p < 0.05$  vs. NT1.

<sup>#</sup>:  $p < 0.05$  vs. NT1 and NT2.

NT1, uncoated MWCNT; NT2, MWCNT coated with carboxylic polyacid polymer; NT3, MWCNT coated with polystyrene polybutadiene polymethylacrylate polymer.

Histological studies of the lungs 24 h after instillation showed the presence of widespread micrometric MWCNT agglomerates, which were mainly located in the bronchiolar lumen and alveolar ducts with NT1 and near the bronchioles and in the alveoli with NT2. NT3 agglomerates were scarce and confined to the alveoli (Figure 6a and 6b). Agglomerate size was greatest with NT1 and smallest with NT3, whereas agglomerate number was greatest with NT2 and smallest with NT3 (Figure 6c). After 1 week,

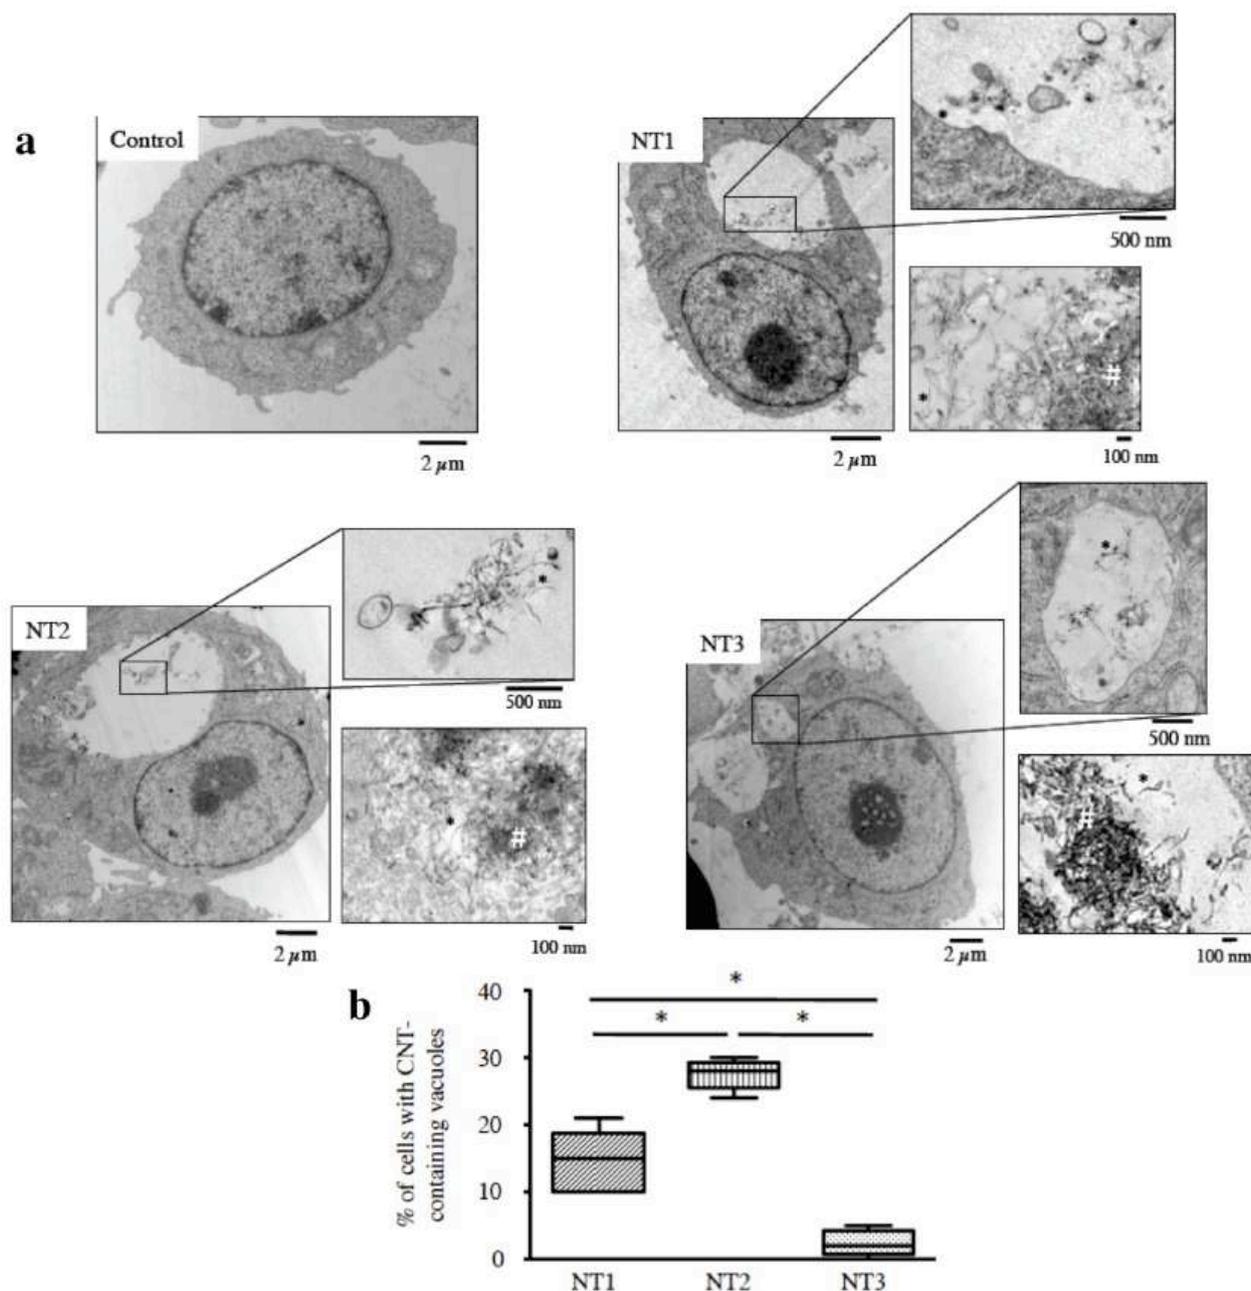


**Figure 3** Effects of MWCNT on macrophages *in vitro* - TEM observations. **Panel a:** Representative transmission electron microscopy (TEM) images of RAW 264.7 cells exposed for 24 h to culture medium alone (Control), or 10  $\mu\text{g/ml}$  of NT1, NT2, or NT3. Inserts show details. \*: example of individual carbon nanotubes. #: example of carbon nanotube agglomerates. Abbreviations are the same as in Figure 1. **Panel b:** Quantification of cells with carbon nanotube-containing vacuoles, expressed as the percentage of the total number of cells. Results are represented as box and whisker plots of values from five fields. Abbreviations are the same as in Figure 1, \*:  $p < 0.05$ .

clusters of cells surrounding visible MWCNT agglomerates were seen in the lungs of animals exposed to NT1 or NT2. These clusters were mainly located near the terminal bronchioles but were also found in the alveolar ducts and alveoli. They were still present 6 months post-exposure (Additional file 5, 6, 7, 8, 9, and 10 figures S5, S6, S7, S8,

S9, and S10). No evidence of fibrosis was found with any of the three MWCNT.


The mRNA expression of various genes implicated in oxidative stress, inflammation, and fibrosis was quantified in lung homogenates, as for the *in vitro* experiments. Significant increases in lung mRNA expression

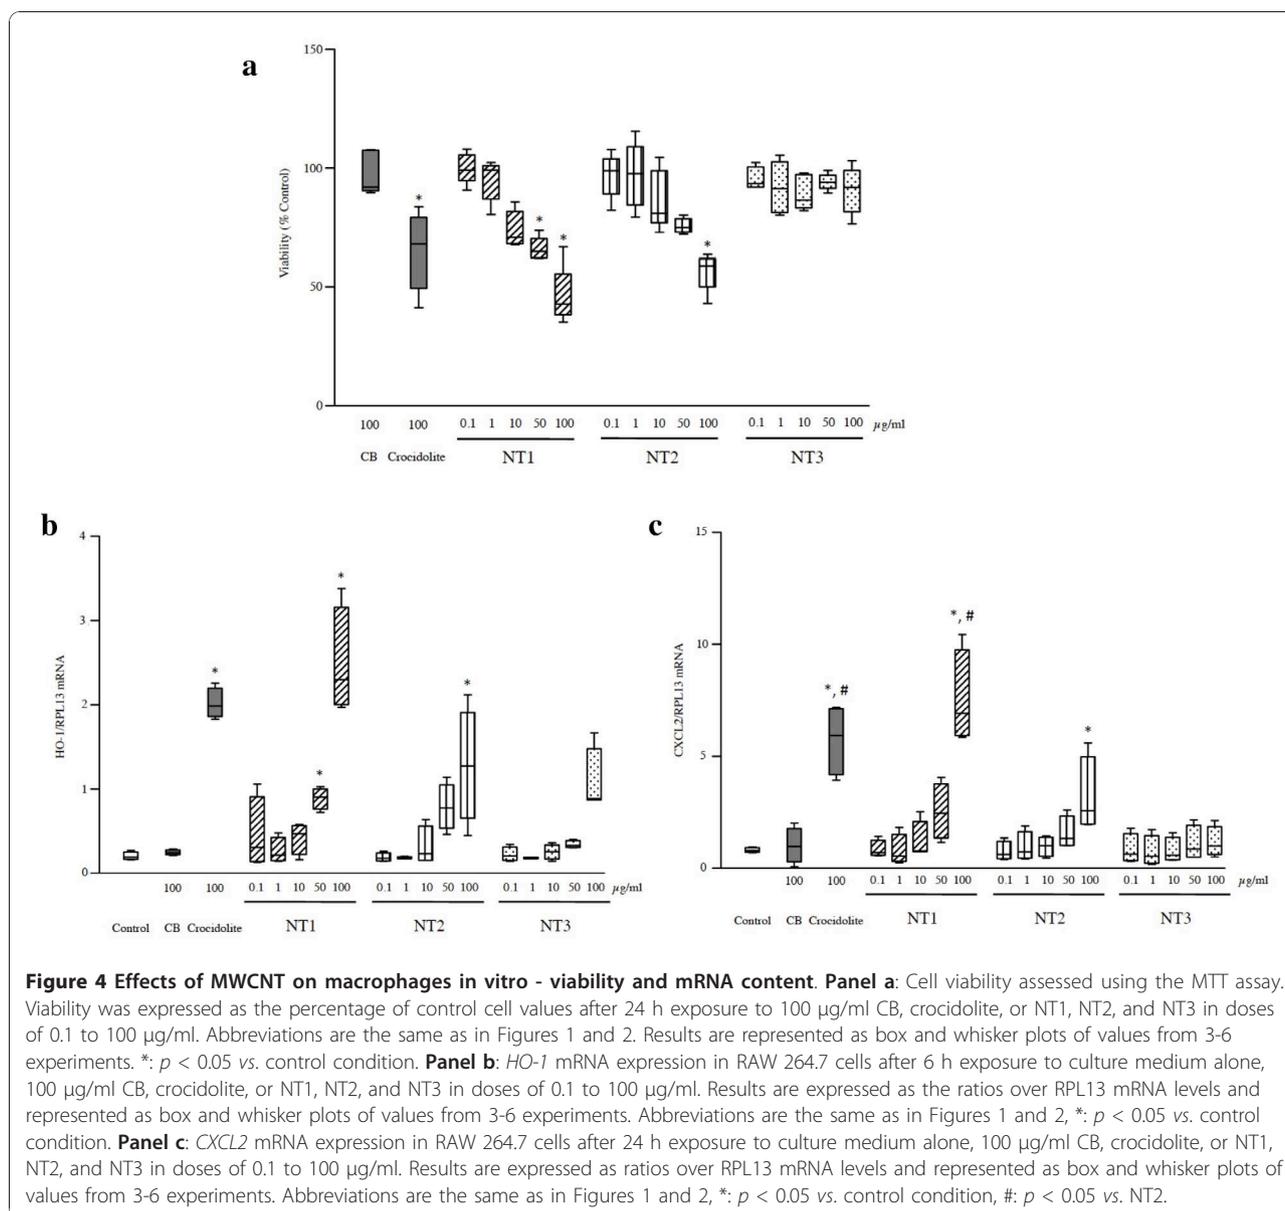

of *SOD-2* and *HO-1*, *TNF- $\alpha$*  and *CXCL2*, and *collagen-1* and -3 were observed between 1 day and 1 week post-instillation in animals exposed to NT2, compared to control animals ( $p < 0.05$  for all comparisons, Figure 7d and data not shown). The expression of these genes returned to basal levels by 1 month post-instillation, except for *HO-1* whose expression returned to basal levels only after 3 months (see Figure 7e for values at 6 months). No modifications in gene expression were seen in animals exposed to NT1, NT3 or polymers alone (data not shown). With none of the three MWCNT did changes occur in the expression of *GPX-1*, *SOD-1*, or *TGF- $\beta$*  mRNA (data not shown).

## Discussion


Taken together, these results show that coating MWCNT with an acidic polymer reduced their specific surface five-fold but enhanced their dispersion in culture medium and their internalization by macrophages both *in vitro* and *in vivo*, compared to uncoated MWCNT. These results agree with earlier data [33] showing that the presence of acidic groups such as phenolic or carboxyl groups on the surface of carbon materials facilitates the internalization of these materials by mouse macrophages. The marked internalization of NT2 by mouse macrophages in our study was associated with the induction of a cytotoxic,

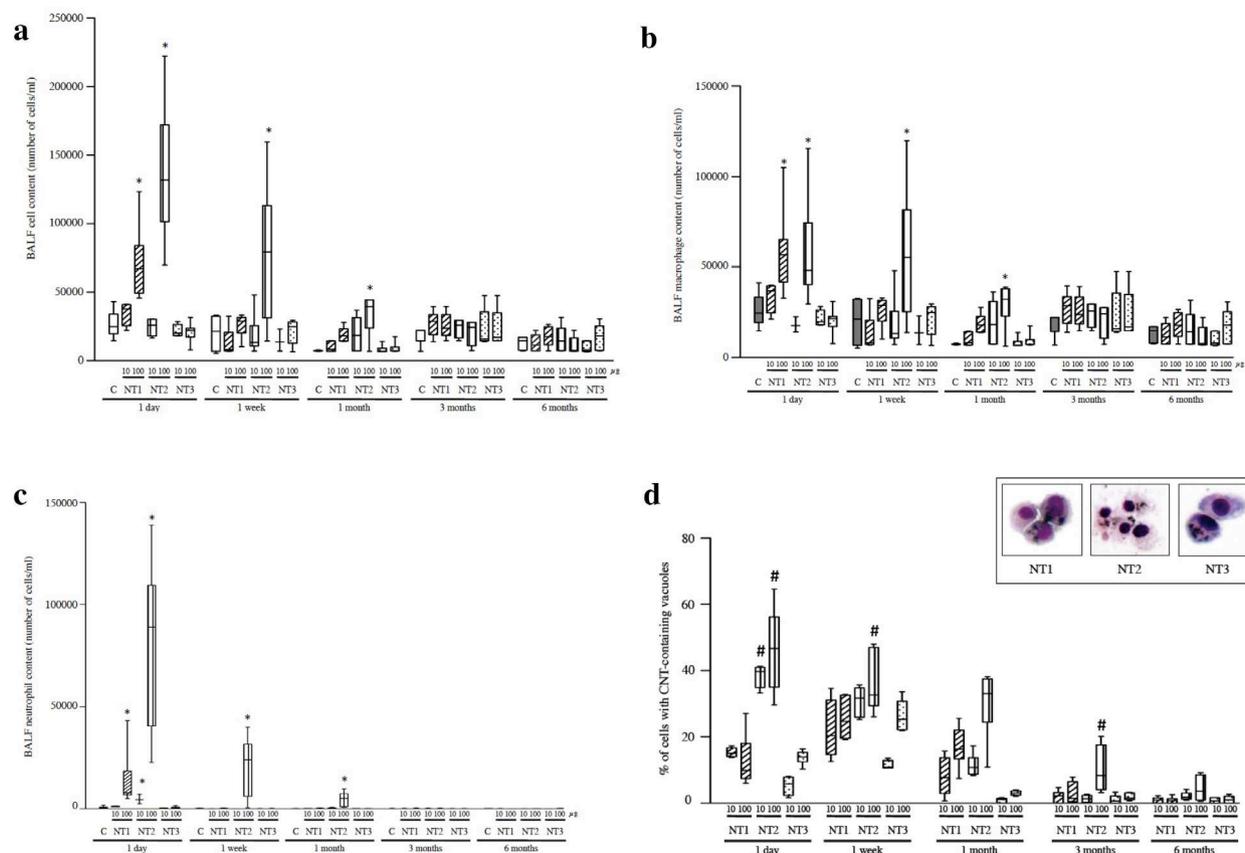

**Figure 5 Effects of MWCNT in vivo in mice - BALF analysis.** **Panel a:** Effect of NT1, NT2 or NT3 in a dose of 10 or 100 µg/mouse on total cell content of bronchoalveolar lavage fluid (BALF) after 1 to 180 days' exposure. Results are represented as box and whisker plots of values from 4-6 animals per group. Abbreviations are the same as in Figures 1 and 2. \*:  $p < 0.05$  compared to control mice. **Panel b:** Effect of NT1, NT2, or NT3 (10 or 100 µg/mouse) on total BALF macrophage content after 1 to 180 days' exposure. Results are represented as box and whisker plots of values from 4-6 animals per group. Abbreviations are the same as in Figures 1 and 2. \*:  $p < 0.05$  compared to control mice. **Panel c:** Effect of NT1, NT2, or NT3 (10 or 100 µg/mouse) on total BAL fluid neutrophil content after 1 to 180 days' exposure. Results are represented as box and whisker plots of values from 4-6 animals per group. Abbreviations are the same as in Figures 1 and 2. \*:  $p < 0.05$  compared to control mice. **Panel d:** Quantification of BAL macrophages with internalized carbon nanotubes, expressed as the percentage of the total macrophage number. Results are represented as box and whisker plots of values obtained from 4-6 animals per group. #:  $p < 0.05$  vs. NT1 and NT3. Insert: representative light microscopy images of BAL cells after 1 day's exposure to 100 µg/mouse of NT1, NT2, or NT3 (magnification  $\times 40$ ). Abbreviations are the same as in Figure 1.

oxidative, and inflammatory response despite the marked decrease in specific surface, compared to NT1. A similar direct relationship between the degree of internalization and the severity of the inflammatory response was described with metallic nanoparticles [34]. In contrast to the *in vitro* experiments, in which the oxidative and inflammatory effects of NT1 and NT2 were similar, the *in vivo* experiments showed stronger oxidative and inflammatory responses to NT2 than to NT1, suggesting that cells other than macrophages were involved in the response to NT2 *in vivo*. This hypothesis is supported by the smaller size and

larger number of NT2 agglomerates in the alveolar wall, suggesting enhanced contact of alveolar cells with NT2 compared to NT1. Accordingly, Shvedova and coworkers [35] demonstrated that exposure of mice to relatively well-dispersed single-walled CNT by inhalation produced a stronger inflammatory response than did pharyngeal aspiration of an agglomerated particle suspension (micrometer-size agglomerates). A stronger inflammatory response to NT2 could result from their acidic surface, in addition to their better internalization. Indeed, we recently obtained data showing that the inflammatory response of murine

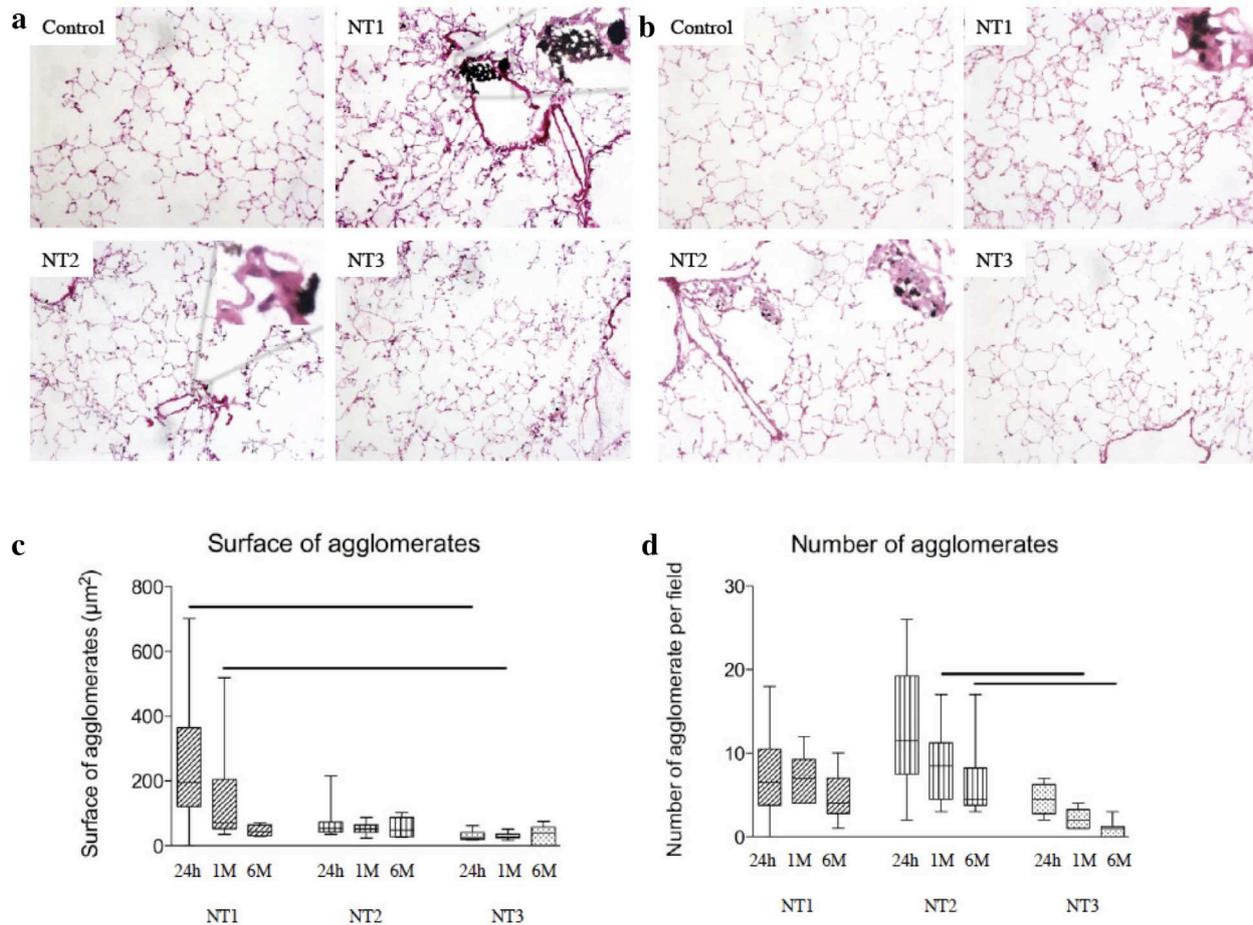


**Figure 6 Effects of MWCNT in vivo in mice - lung histology.** **Panel a:** Lung histology 1 day after a single intratracheal instillation of vehicle or NT1, NT2 or NT3 (100 µg/mouse, magnification ×20). Abbreviations are the same as in Figure 1. Inserts are higher magnification views (×40) of the carbon nanotube agglomerates. **Panel b:** Lung histology 30 days after a single intratracheal instillation of vehicle, NT1, NT2, or NT3 (100 µg/mouse, magnification ×20). Abbreviations are the same as in Figure 1. Inserts are higher magnification views (×40) of carbon nanotube agglomerates. **Panel c:** Quantification of the number and size of carbon nanotube agglomerates in lungs of mice 24 hours, 1 month, or 6 months after a single intratracheal instillation of 100 µg NT1, NT2, or NT3. Results are represented as box and whisker plots of values from 5 animals (five fields per animal). \*:  $p < 0.05$  between groups.

macrophages exposed to MWCNT generated by catalyst chemical vapor deposition was more marked when acidic groups were present on the MWCNT surface, compared to identically produced MWCNT of similar length that did not have acidic groups on their surface (Cyrill Bussy, unpublished data). Moreover, Hamilton and colleagues [36] recently showed that titanium dioxide nanoparticles induced inflammasome activation and inflammatory cytokine release through a cathepsin B-mediated mechanism involving lysosomal disruption and, therefore, acidification of the intracellular compartment, thus linking acidification to inflammatory response. It should be noted, however, that the inflammatory response to NT2, evaluated based on BAL fluid cellularity and lung gene expression, resolved between 1 week and 1 month post-instillation, which

probably explained the absence of persistent histological abnormalities. The absence of fibrosis may also reflect the strain of mice used in this study as compared to others [37].

In contrast to the acidic polymer, the polystyrene polymer suppressed the cytotoxicity, oxidative stress, and inflammation observed both *in vitro* and *in vivo* when the nanotubes were not coated. Several mechanisms may explain this result. First, the coated MWCNT contained 50% polymer by weight and therefore contained half the amount of nanotube material supplied by NT1. To investigate the potential role for this difference, we performed *in vivo* experiments, comparing the effects of 100 µg of NT1 to those of a “double dose” of NT2 and NT3 (200 µg, thus containing the same amount of MWCNT than 100 µg of

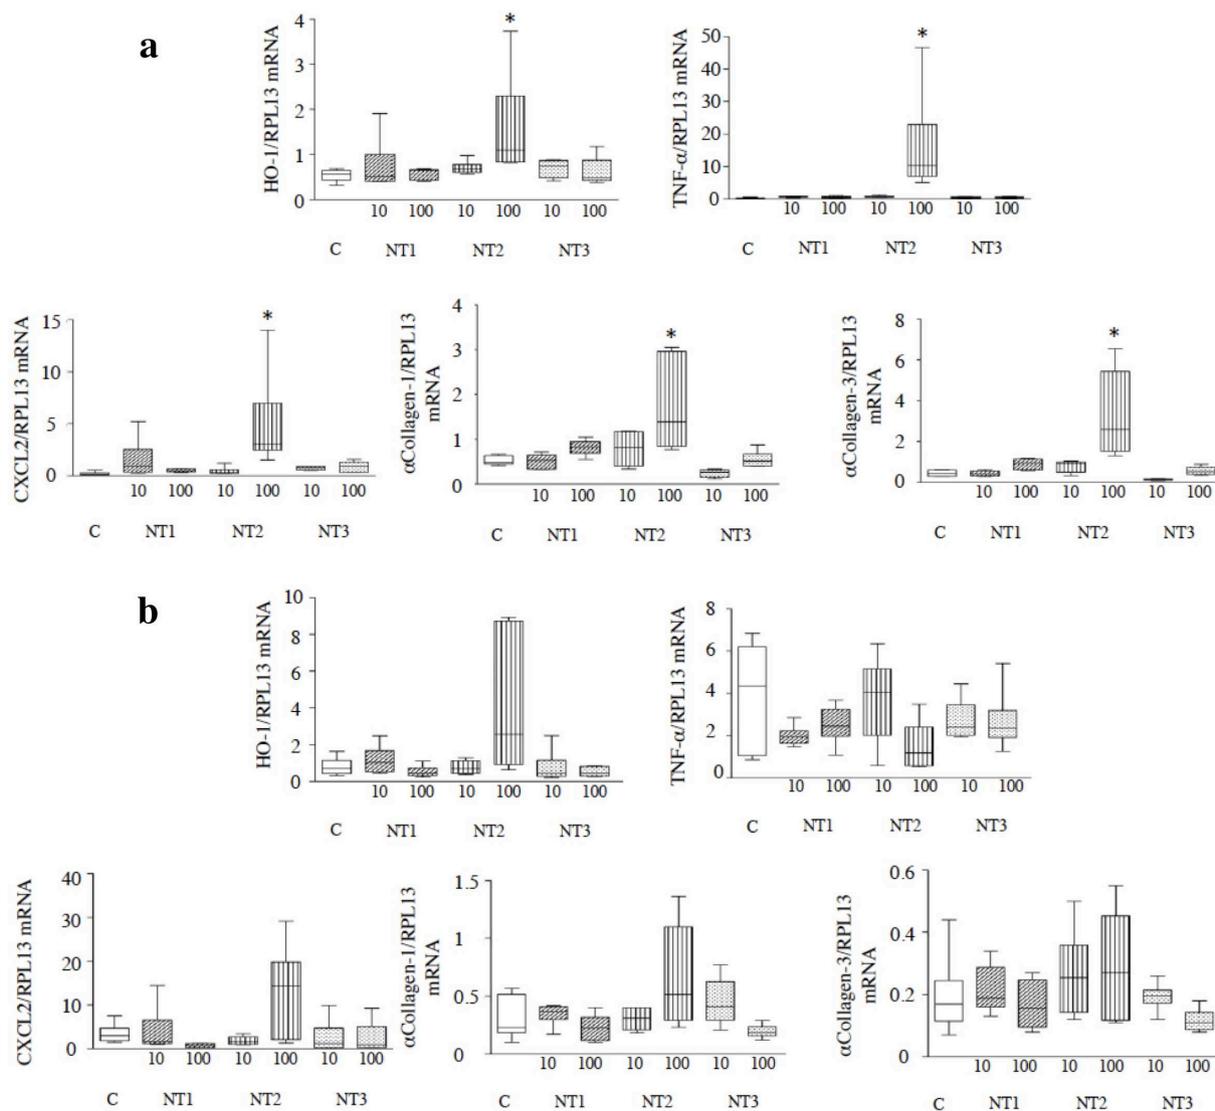

**Figure 7 Effects of MWCNT in vivo in mice - lung mRNA content.** Panel a: *HO-1*, *TNF- $\alpha$* , *CXCL2*,  *$\alpha$ -collagen-1*, and  *$\alpha$ -collagen-3* mRNA expression in the lungs of mice 7 days after intratracheal instillation of vehicle or of 10 or 100  $\mu$ g of NT1, NT2, or NT3. Results are expressed as the ratios over RPL13 mRNA levels and represented as box and whisker plots of values from 5-6 animals. Abbreviations are the same as in Figure 1. \*:  $p < 0.05$  vs. control condition. Panel b: *HO-1*, *TNF- $\alpha$* , *CXCL2*,  *$\alpha$ -collagen-1*, and  *$\alpha$ -collagen-3* mRNA expression in the lungs of mice 180 days after intratracheal instillation of vehicle or of 10 or 100  $\mu$ g of NT1, NT2, or NT3. Results are expressed as the ratios over RPL13 mRNA levels and represented as box and whisker plots of values from 5-6 animals. Abbreviations are the same as in Figure 1.

NT1). These experiments showed that BAL fluid cellularity 24 h after exposure to 200  $\mu$ g NT2 or NT3 was similar to that seen with the original dose of 100  $\mu$ g (data not shown), excluding a role for reduced MWCNT mass in the absence of NT3 toxicity. Second, the specific surface area was smaller with the coated MWCNT than with NT1. However, NT2 and NT3 had similar specific surface areas, yet different toxicities. Third, cell internalization was less marked with NT3 than with the other MWCNT. Similarly, Pan and co-workers [38] showed that coating TiO<sub>2</sub> nanoparticles

with a dense grafted polymer brush that exhibited hydrophobic properties, also exhibited by our NT3, prevented adherence to the cell membrane and hence penetration into the cell and induction of oxidative stress. Indeed, cells adhere less well to hydrophobic than to hydrophilic biomaterials [39]. However, the reduced internalization of NT3 was probably not the only mechanism explaining the absence of toxicity of this material, since the *in vivo* experiments showed similar numbers of alveolar macrophages with MWCNT-containing vacuoles in the NT1 and NT3

groups. Fourth, NT3 may have a decreased ability to induce an oxidative and inflammatory response once internalized, compared to the other two MWCNT. This mechanism is consistent with the presence on the NT3 surface of large numbers of ozone oxidizable groups, compared to the other two MWCNT. These oxidizable groups may act as free radical scavengers [40] thereby decreasing the oxidative stress and consecutive inflammation in NT3-exposed cells and animals. Further studies are needed to determine whether such a mechanism is at play.

We administered MWCNT intratracheally to investigate their effects on the lung. We are aware that inhalation should be preferred over intratracheal instillation for toxicological investigations [41] but we believe our study is relevant to the analysis of the importance of surface characteristics as a determinant of MWCNT toxicity, as we compared the effects of the three materials administered to mice in the same way and using the same experimental set-up. Furthermore, the consistency of the results from our simultaneous *in vitro* and *in vivo* investigations supports the validity of our findings.

## Conclusions

In conclusion, to the best of our knowledge, this study supplies the first evidence that using polymer-coating is a useful strategy to diminish adverse effects of CNT. Such tool to modify the surface environment of industrially produced CNT may hold promise for improving occupational safety, as well as general user's safety.

## Additional material

**Additional file 1: Representative scanning electron microscopy (SEM) of CNT uncoated (NT1) and coated with carboxylic polyacid or polystyrene polybutadiene polymethacrylate of methyl polymers (NT2 and NT3 respectively).**

**Additional file 2: Representative transmission electronic microscopy (TEM) images of RAW 264.7 cells exposed for 24 h to 10 µg/ml of NT1. Panel a:** focus is performed on cellular structures. **Panel b:** focus is performed on individual CNT inside the cell. Abbreviations are the same as in Figure 1.

**Additional file 3: Cell viability assessed by MTT assay.** Viability was expressed as a percentage of control cell values, after 6h exposure to 100 µg/ml CB, Crocidolite, or 0.1 to 100 µg/ml NT1, NT2 or NT3. Abbreviations are the same as in Figure 1 and 2. Results are represented as box and whiskers for values obtained in 3-6 experiments. \*:  $p < 0.05$  vs control condition.

**Additional file 4: Cell viability assessed by MTT assay.** Viability was expressed as a percentage of control cell values, after 24h exposure to Polymers alone (Carb. Pol.: carboxylic polyacid polymer, PMMA Pol.: polystyrene polybutadiene polymethylmethacrylate polymer), or 100 µg/ml CB, Crocidolite, NT1, NT2 or NT3. Abbreviations are the same as in Figure 1 and 2. Results are represented as box and whiskers for values obtained in 3-6 experiments. \*:  $p < 0.05$  vs control condition.

**Additional file 5: Effect of NT1, NT2 or NT3 in a dose of 100 or 200 µg/mouse on total cell content of bronchoalveolar lavage fluid**

**(BALF) after 1 day exposure.** Results are represented as box and whisker plots of values from 4-6 animals per group. Abbreviations are the same as in Additional file 4. \*:  $p < 0.05$  compared to control mice.

**Additional file 6: Representative optical microscopy images of cells from BAL after 1 day exposure to CNT vehicle or 100 µg/mouse NT1, NT2 or NT3 (magnification ×10).** Abbreviations are the same as in Figure 1 and 2.

**Additional file 7: Lung histology 1 week after a single intratracheal instillation of CNT vehicle or NT1, NT2 or NT3 (100 µg/mouse, magnification ×20).** Abbreviations are the same as in Figure 1 and 2. Inserts are higher magnification (×40) of CNT agglomerates.

**Additional file 8: Lung histology 3 months after a single intratracheal instillation of CNT vehicle or NT1, NT2 or NT3 (100 µg/mouse, magnification ×20).** Abbreviations are the same as in Figure 1 and 2. Inserts are higher magnification (×40) of CNT agglomerates.

**Additional file 9: Lung histology 6 months after a single intratracheal instillation of CNT vehicle or NT1, NT2 or NT3 (100 µg/mouse, magnification ×20).** Abbreviations are the same as in Figure 1 and 2. Inserts are higher magnification (×40) of CNT agglomerates.

**Additional file 10: Higher magnification (×40) of clusters of cells surrounding visible NT1 (left panel) or NT2 (right panel) agglomerates, 1 month post-instillation.**

## Acknowledgements

Lyes Tabet was a recipient of a joint grant from ADEME (Agence de l'Environnement et de la Maitrise de l'Énergie) and ARKEMA. The authors thank Olivier Thibaudeau (Plate-Forme de Morphologie, Hôpital Bichat) for his assistance in preparing the anatomic specimens and Héléne Desqueyroux (ADEME) for her helpful comments.

## Author details

<sup>1</sup>INSERM U955, Créteil, F-94010 France, and Université Paris Est Val de Marne (UPEC), Créteil, F-94010, France. <sup>2</sup>Institut universitaire romand de Santé au Travail (Institute for Work and Health), Université de Lausanne et Université de Genève, Rue du Bugnon 21, CH-1011 Lausanne, Switzerland. <sup>3</sup>Laboratory of atmospheric chemistry (LAC), Paul Scherrer Institut (PSI), OFLA008, CH-5232 Villigen PSI, Switzerland. <sup>4</sup>AP-HP, Hôpital Henri Mondor, Service de Physiologie Explorations Fonctionnelles, 94010 Créteil, France. <sup>5</sup>Hôpital Intercommunal de Créteil, Service de pneumologie et pathologie professionnelle, Créteil, 94000, France. <sup>6</sup>Department of Environmental Toxicology, University of California, Davis, CA 95616, USA.

## Authors' contributions

LT, CB, JB, and SL designed the study. LT, CB and ASD performed the biological assays. AS and MR performed the physicochemical measurements. JB and SL drafted the manuscript, and CB and MR helped with the final version. All authors read and approved the final manuscript.

## Competing interests

The authors declare that they have no competing interests.

Received: 14 September 2010 Accepted: 21 January 2011

Published: 21 January 2011

## References

1. Simeonova PP: Update on carbon nanotube toxicity. *Nanomed* 2009, **4**:373-375.
2. Shvedova AA, Kagan VE, Fadeel B: Close encounters of the small kind: adverse effects of man-made materials interfacing with the nanocosmos of biological systems. *Annu Rev Pharmacol Toxicol* 2010, **50**:63-88.
3. Oberdörster G: Safety assessment for nanotechnology and nanomedicine: concepts of nanotoxicology. *Journal of Internal Medicine* 2010, **267**:89-105.
4. Warheit DB, Sayes CM, Reed KL, Swain KA: Health effects related to nanoparticle exposures: Environmental, health and safety considerations for assessing hazards and risks. *Pharmacol Ther* 2008, **120**:35-42.

5. Li Z, Hulderman T, Salmen R, Chapman R, Leonard SS, Young SH, Shvedova A, Luster MI, Simeonova PP: **Cardiovascular effects of pulmonary exposure to single-wall carbon nanotubes.** *Environ Health Perspect* 2007, **115**:377-382.
6. Helland A, Wick P, Koehler A, Schmid K, Som C: **Reviewing the environmental and human health knowledge base of carbon nanotubes.** *Environ Health Perspect* 2007, **115**:1125-1131.
7. Nemmar A, Hoylaerts MF, Hoet PH, Dinsdale D, Smith T, Xu H, Vermeylen J, Nemery B: **Ultrafine particles affect experimental thrombosis in an in vivo hamster model.** *Am J Respir Crit Care Med* 2002, **166**:998-1004.
8. Nemmar A, Vanbilloen H, Hoylaerts MF, Hoet PH, Verbruggen A, Nemery B: **Passage of intratracheally instilled ultrafine particles from the lung into the systemic circulation in hamster.** *Am J Respir Crit Care Med* 2001, **164**:1665-1668.
9. Brown J, Zeman K, Bennett W: **Ultrafine particle deposition and clearance in the healthy and obstructed lung.** *Am J Respir Crit Care Med* 2002, **166**:1240-1247.
10. Nel A, Xia T, Madler L, Li N: **Toxic potential of materials at the nanolevel.** *Science* 2006, **311**:622-627.
11. Poland CA, Duffin R, Kinloch I, Maynard A, Wallace WA, Seaton A, Stone V, Brown S, Macnee W, Donaldson K: **Carbon nanotubes introduced into the abdominal cavity of mice show asbestos-like pathogenicity in a pilot study.** *Nat Nanotechnol* 2008, **3**:423-428.
12. Lam CW, James JT, McCluskey R, Arepalli S, Hunter RL: **A review of carbon nanotube toxicity and assessment of potential occupational and environmental health risks.** *Crit Rev Toxicol* 2006, **36**:189-217.
13. Stern ST, McNeil SE: **Nanotechnology safety concerns revisited.** *Toxicol Sci* 2008, **101**:4-21.
14. Sydlík U, Gallitz I, Albrecht C, Abel J, Krutmann J, Unfried K: **The compatible solute ectoine protects against nanoparticle-induced neutrophilic lung inflammation.** *Am J Respir Crit Care Med* 2009, **180**:29-35.
15. Fenoglio I, Greco G, Tomatis M, Muller J, Raymundo-Pinero E, Beguin F, Fonseca A, Nagy JB, Lison D, Fubini B: **Structural defects play a major role in the acute lung toxicity of multiwall carbon nanotubes: physicochemical aspects.** *Chem Res Toxicol* 2008, **21**:1690-1697.
16. Johnston HJ, Hutchison GR, Christensen FM, Peters S, Hankin S, Aschberger K, Stone V: **A critical review of the biological mechanisms underlying the in vivo and in vitro toxicity of carbon nanotubes: The contribution of physico-chemical characteristics.** *Nanotoxicology* 2010, **4**:207-246.
17. Kayat J, Gajbhiye V, Tekade RK, Jain NK: **Pulmonary toxicity of carbon nanotubes: a systematic report.** *Nanomedicine* 2010, **xx**:1-10.
18. Tong H, McGee JK, Saxena RK, Kodavanti UP, Devlin RB, Gilmour MI: **Influence of acid functionalization on the cardiopulmonary toxicity of carbon nanotubes and carbon black particles in mice.** *Toxicol Appl Pharmacol* 2009, **239**:224-232.
19. Vittorio O, Raffa V, Cuschieri A: **Influence of purity and surface oxidation on cytotoxicity of multi-wall carbon nanotubes with human neuroblastoma cells.** *Nanomedicine* 2009, **5**:424-431.
20. Ciobanu M, Siove A, Gueguen V, Gamble LJ, Castner DG, Migonney V: **Radical graft polymerization of styrene sulfonate on poly(ethylene terephthalate) films for ACL applications: "grafting from" and chemical characterization.** *Biomacromolecules* 2006, **7**:755-760.
21. Rossi MJ, Demirdjian B: **The surface properties of SOA generated from limonene and toluene using specific molecular probes: exploration of a new experimental technique.** *Atmos Chem Phys Discuss* 2005, **5**:1-48.
22. Setyan A, Sauvain JJ, Rossi MJ: **The use of heterogeneous chemistry for the characterization of functional groups at the gas/particle interface of soot and TiO<sub>2</sub> nanoparticles.** *Phys Chem Chem Phys* 2009, **11**:6205-6217.
23. Tabet L, Bussy C, Amara N, Setyan A, Grodet A, Rossi MJ, Pairon JC, Boczkowski J, Lanone S: **Adverse effects of industrial multiwalled carbon nanotubes on human pulmonary cells.** *J Toxicol Environ Health A* 2009, **72**:60-73.
24. Bussy C, Cambedouzou J, Lanone S, Leccia E, Heresanu V, Pinault M, Mayne-L'hermite M, Brun N, Mory C, Cotte M, et al: **Carbon Nanotubes in Macrophages: Imaging and Chemical Analysis by X-ray Fluorescence Microscopy.** *Nano Lett* 2008, **8**:2659-2663.
25. Herzog E, Byrne HJ, Davoren M, Casey A, Duschl A, Oostingh GJ: **Dispersion medium modulates oxidative stress response of human lung epithelial cells upon exposure to carbon nanomaterial samples.** *Toxicol Appl Pharmacol* 2009, **236**:276-281.
26. Worle-Knirsch JM, Pulskamp K, Krug HF: **Oops they did it again! Carbon nanotubes hoax scientists in viability assays.** *Nano Lett* 2006, **6**:1261-1268.
27. Oberdörster G, Yu CP: **Lung dosimetry - Considerations for noninhalation studies.** *Exp Lung Res* 1999, **25**:1-6.
28. Bachoual R, Boczkowski J, Goven D, Amara N, Tabet L, On D, Lecon-Malas V, Aubier M, Lanone S: **Biological effects of particles from the paris subway system.** *Chem Res Toxicol* 2007, **20**:1426-1433.
29. Plantier L, Marchand-Adam S, Antico VG, Boyer L, De Coster C, Marchal J, Bachoual R, Mailleux A, Boczkowski J, Crestani B: **Keratinocyte growth factor protects against elastase-induced pulmonary emphysema in mice.** *Am J Physiol Lung Cell Mol Physiol* 2007, **293**:L1230-1239.
30. Davoren M, Herzog E, Casey A, Cottineau B, Chambers G, Byrne HJ, Lyng FM: **In vitro toxicity evaluation of single walled carbon nanotubes on human A549 lung cells.** *Toxicol In Vitro* 2007, **21**:438-448.
31. Muller J, Huaux F, Moreau N, Misson P, Heilier JF, Delos M, Arras M, Fonseca A, Nagy JB, Lison D: **Respiratory toxicity of multi-wall carbon nanotubes.** *Toxicol Appl Pharmacol* 2005, **207**:221-231.
32. Wick P, Manser P, Limbach LK, Dettlaff-Weglikowska U, Krumeich F, Roth S, Stark WJ, Bruinink A: **The degree and kind of agglomeration affect carbon nanotube cytotoxicity.** *Toxicol Lett* 2007, **168**:121-131.
33. Czajkowska B, Blazewicz M: **Phagocytosis of chemically modified carbon materials.** *Biomaterials* 1997, **18**:69-74.
34. Hussain S, Boland S, Baeza-Squiban A, Hamel R, Thomassen LC, Martens JA, Billon-Galland MA, Fleury-Feith J, Moisan F, Pairon JC, Marano F: **Oxidative stress and proinflammatory effects of carbon black and titanium dioxide nanoparticles: role of particle surface area and internalized amount.** *Toxicology* 2009, **260**:142-149.
35. Shvedova AA, Kisin ER, Murray AR, Johnson VJ, Gorelik O, Arepalli S, Hubbs AF, Mercer RR, Keohavong P, Sussman N, et al: **Inhalation Versus Aspiration of Single Walled Carbon Nanotubes in C57bl/6 Mice: Inflammation, Fibrosis, Oxidative Stress and Mutagenesis.** *Am J Physiol Lung Cell Mol Physiol* 2008, **95**:L552-565.
36. Hamilton RF Jr, Wu N, Porter D, Buford M, Wolfarth M, Holian A: **Particle length-dependent titanium dioxide nanomaterials' toxicity and bioactivity.** *Part Fibre Toxicol* 2009, **6**:35.
37. Crouzier D, Follot S, Gentilhomme E, Flahaut E, Arnaud R, Dabouis V, Castellarin C, Debouzy JC: **Carbon nanotubes induce inflammation but decrease the production of reactive oxygen species in lung.** *Toxicology* 2007, **272**:39-45.
38. Pan Z, Lee W, Slutsky L, Clark RA, Pernodet N, Rafailovich MH: **Adverse Effects of Titanium Dioxide Nanoparticles on Human Dermal Fibroblasts and How to Protect Cells.** *Small* 2009, **5**:511-520.
39. Arima Y, Iwata H: **Effect of wettability and surface functional groups on protein adsorption and cell adhesion using well-defined mixed self-assembled monolayers.** *Biomaterials* 2007, **28**:3074-3082.
40. Fenoglio I, Tomatis M, Lison D, Muller J, Fonseca A, Nagy JB, Fubini B: **Reactivity of carbon nanotubes: free radical generation or scavenging activity?** *Free Radic Biol Med* 2006, **40**:1227-1233.
41. Donaldson K, Poland CA: **Nanotoxicology: new insights into nanotubes.** *Nat Nanotechnol* 2009, **4**:708-710.

doi:10.1186/1743-8977-8-3

Cite this article as: Tabet et al: Coating carbon nanotubes with a polystyrene-based polymer protects against pulmonary toxicity. *Particle and Fibre Toxicology* 2011 **8**:3.

**Submit your next manuscript to BioMed Central and take full advantage of:**

- Convenient online submission
- Thorough peer review
- No space constraints or color figure charges
- Immediate publication on acceptance
- Inclusion in PubMed, CAS, Scopus and Google Scholar
- Research which is freely available for redistribution

Submit your manuscript at  
www.biomedcentral.com/submit

